

Test Report

Number: GZHH00492792


Applicant: WOODEVO COMPOSITE DECKING
3 BASS CRT KEYSBOROUGH VIC 3150

Date: Jun 05, 2023

Attn: OWEN

Sample Description:

One (1) submitted sample said to be **WoodEvo Composite Decking** :
Item No. : Home Range / Home+ Range
Date Sample Received : May 15, 2023 & Jun 05, 2023
Testing Period : May 15, 2023 to Jun 05, 2023

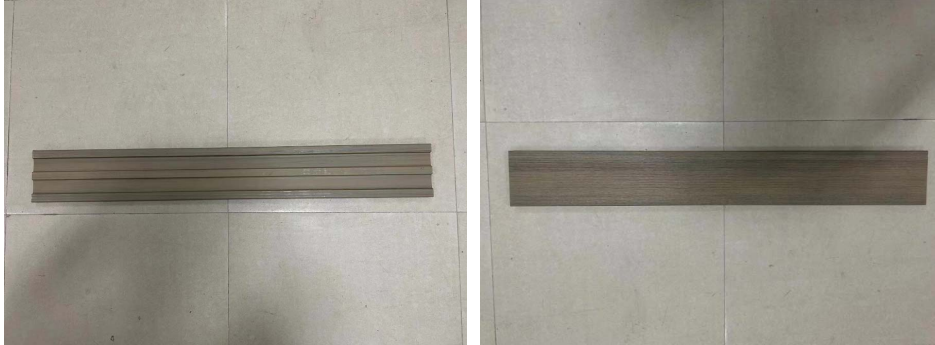

Tests conducted:

As requested by the applicant, refer to attached page(s) for details.

Conclusion:

<u>Tested sample</u>	<u>Test item</u>	<u>Result</u>
Submitted samples	Reaction to fire tests for floorings - As per AS ISO 9239.1-2003(R2016)	See test conducted

Authorized by:
For Intertek Testing Services Shenzhen Ltd.
Guangzhou Branch, Hardlines

Victor T.J. Wang
Assistant General Manager



Test Report

Number: GZHH00492792

Tests Conducted

1 Reaction to fire tests for floorings

As per AS ISO 9239.1-2003(R2016) Reaction to fire tests for floorings-Part 1: Determination of the burning behaviour using a radiant heat source, the submitted samples were subjected to the following tests:

Sample description: WoodEvo Composite Decking

Initial inspection: No any damage was found.

Executive summary:

Tested Item	Test methods	Test result
Critical heat flux (CHF)	Test method: As per AS ISO 9239.1-2003(R2016) Profile type: solid	Length direction: 6.4kW/m ² Width direction: 6.9kW/m ²
Smoke production	Specimen size: 1050 mm×230 mm Pre-Conditioning: 23±2°C, 50±5%RH. 74h	453.3%×min

The statements of conformity reported have considered the decision rule agreed, namely that Intertek have taken account of measurement uncertainty as calculated by Intertek, and applied according to ILAC-G8/09:2019 (Non-binary acceptance based on guard band $w = U$) except designation from the customer, regulation or test specification. This decision rule only applies to the numeric test results.

The sample(s) and sample information hereto are provided by the client who shall be solely responsible for the authenticity and integrity thereof. The results shown in this report relate only to the sample(s) tested. It is not intended to be a recommendation for any particular course of action. Intertek does not accept a duty of care or any other responsibility to any person other than the Client in respect of this report and only accepts liability to the Client insofar as is expressly contained in the terms and conditions governing Intertek's provision of services to you. Intertek makes no warranties or representations either express or implied with respect to this report save as provided for in those terms and conditions. We have aimed to conduct the Review on a diligent and careful basis and we do not accept any liability to you for any loss arising out of or in connection with this report, in contract, tort, by statute or otherwise, except in the event of our gross negligence or wilful misconduct. This report shall not be reproduced unless with prior written approval from Intertek Testing Services Shenzhen Limited, Guangzhou Branch. The testing data and result issued by this report are just for scientific research, teaching, internal quality control, product research and development etc. on reference only in the territory of the People's Republic of China.

